

# **Production status of Test Gaps for RE4 RPCs in Upscope**

***K. S. Lee, S. Park @KODEL***

## **Contents**


- 1. Oil dirt on HPL surfaces**
- 2. Oiled layers**
- 3. Silk data for RE4/2 test gaps**
- 4. First HV data for RE4/2 test gaps**

# 1. Oil dirt on HPL surfaces


**Checked that oil dirt remained on all the HPLs (all batches)**

- Found that the stripe pattern created by the cleaning procedure was barely visible and just partially performed.
- At some places of the HPL sheets , the oil dirt still remained was thick.

**Before cleaning**

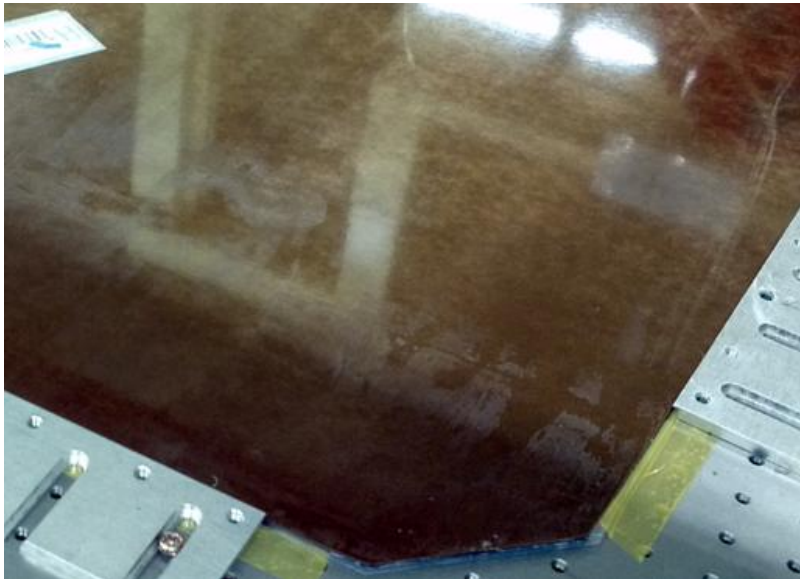

**After cleaning by IPA only**

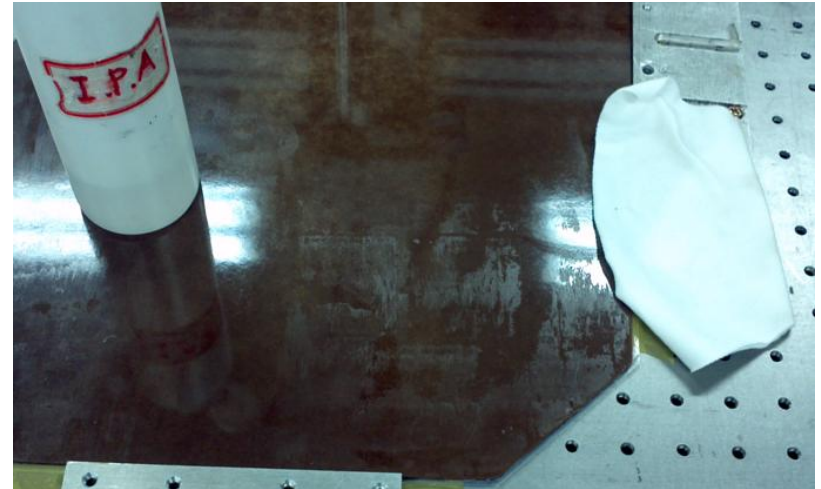


**After cleaning by thinner**



## 2. Oiled layers

- Opened a RE4/2 test bottom gap (HPLs from batch 12)
- The bonding strength seems to be good enough, but the surface layer of the HPLs were easy detached like a stacked paper layer. (**HPLs are mechanically fragile !**)
  - > Phenol resin seems to be very poorly smeared into the craft papers.  
Spacers were detached due to lack of the rigidity of the HPLs
- Places where the phenol resin was well smeared -> dark  
Otherwise -> bright and having microscopic bright spots

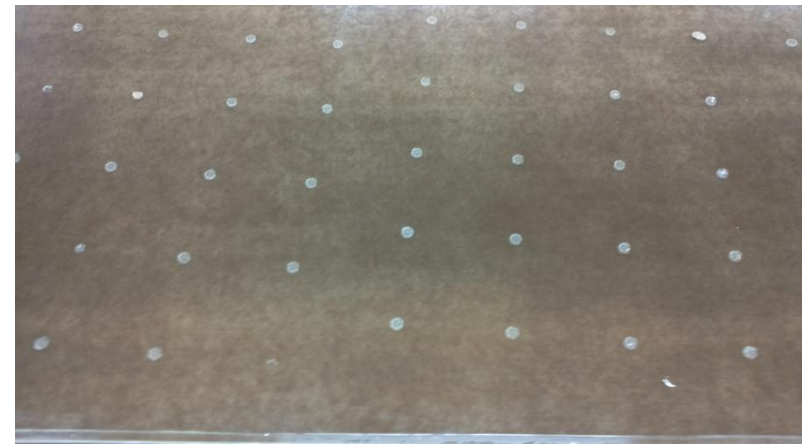




- We expect that the oil pattern could be nicely formed only when the oil/heptane is well attached on the phenol-covered surface of the HPL.




- Bad condensation of the oil could be due to two different factors

- 1) Oil dirt (microscopically thin layer remained even after cleaned by IPA and thinner)  
(Still greasy even after cleaning by thinner & IPA)
- 2) Poor condition of smeared phenol resin into the craft papers  
(The color is brighter and having white microscopic spots)

**Bad oiled patterns especially on the places that the phenol was poorly smeared.**

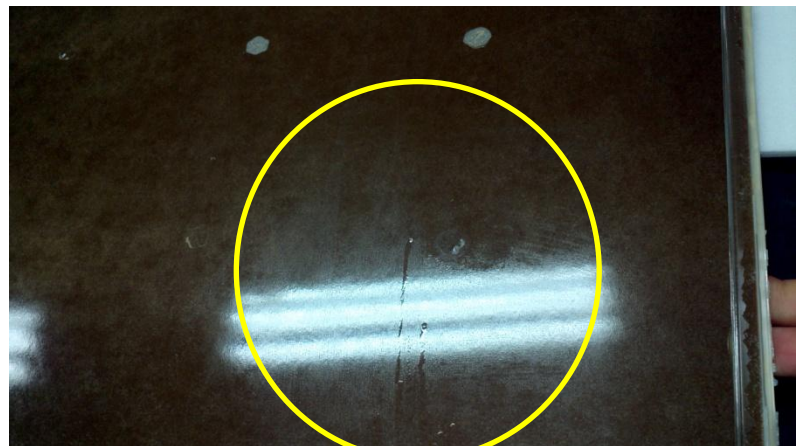

Good oiled patterns on the places that the phenol was relatively well smeared.

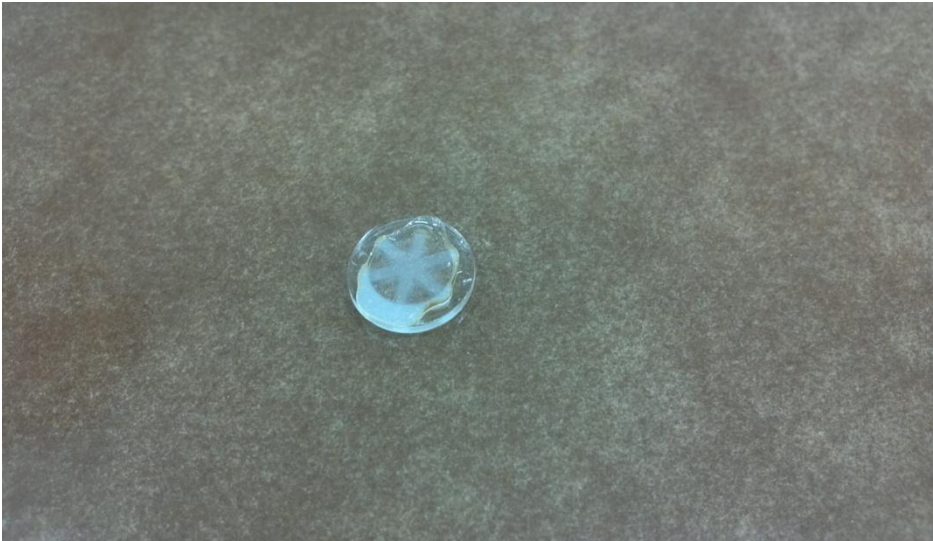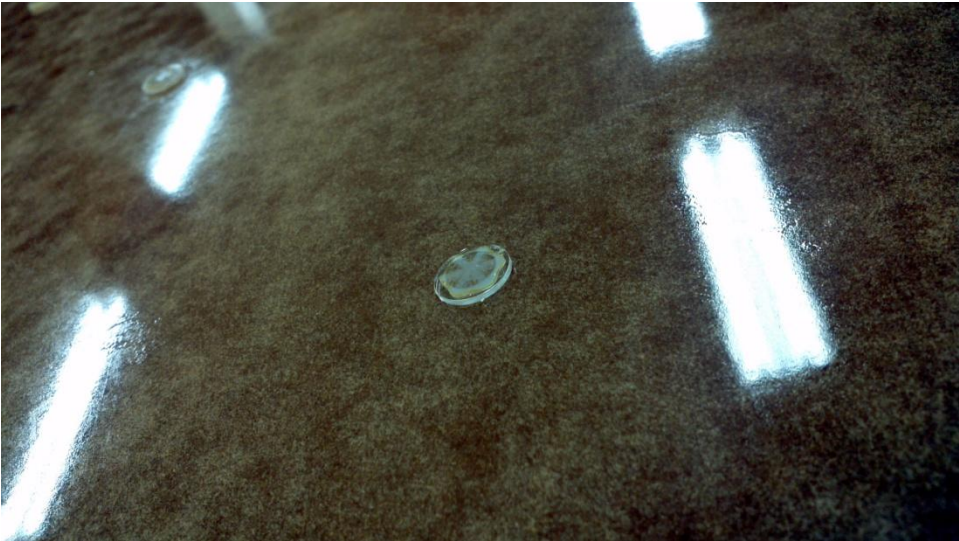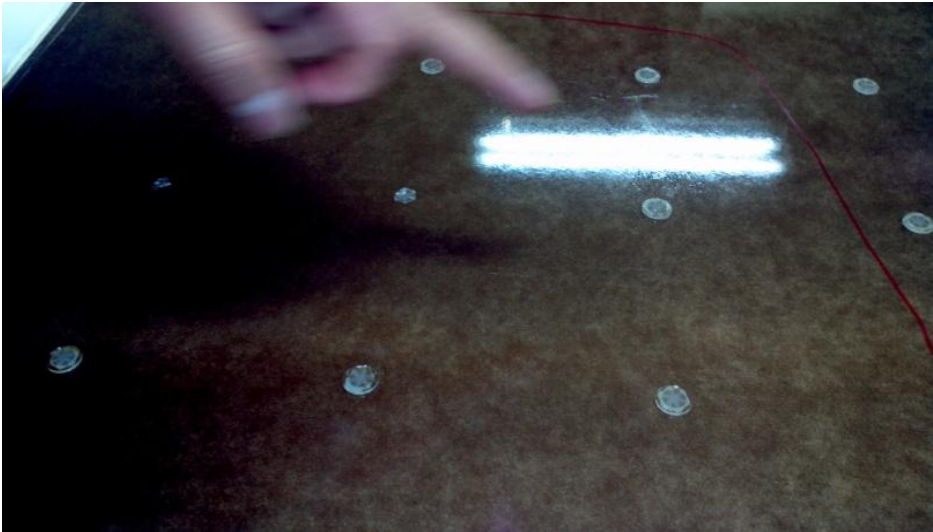





# 4. First HV data for RE4/2 test gaps

- The first HV test for 10 RE4/2 test bottom gaps was very successful.

- One gap was disconnected from HV cabling at somewhere  
-> drop it !

- All the rest 9 gaps were QC certified !

- At 6.0 kV,  $i \sim 0.2 \mu\text{A}$  for all the gaps  
At 10.0 kV, maximum  $i = 0.74 \mu\text{A}$   
 $i(120\text{h})/i(63\text{h}) < 1.0$  for all the gap

- But we expected the currents of the test gaps should be much smaller than the normal gaps to be built with a right resistivity range ! (the resistivity of the HPLs in batch 12 is much higher)

4. HV tests

$$HV_0(293\text{K}, 1013\text{hPa}) = HV_{\text{applied}} \frac{1013\text{hPa}}{P} \frac{T}{293\text{K}}$$

Starting date of test		Feb. 07, 2012		Total gas rate = /h		Gas	Mixture	
				Circulation bfr HV = 26 h		0.95 Freon	0.05 i-Bu	
Time from test start	Date/ Time	P (hPa)	T (°C)	HV <sub>applied</sub> (kV)	HV <sub>0</sub> (kV)	I <sub>ini</sub> (μA)	I <sub>final</sub> (μA)	H (%)
0.0 h	Feb. 07, 2012 / 19:00	1021.5	18	1	0.98	0.01	0	23
0.5 h	19:30	1021.5	18	2	1.97	0.01	0.01	23
1.0 h	20:00	1021.5	18	3	2.95	0.01	0	23
1.5 h	20:30	1022.3	18	4	3.94	0.02	0.01	23
2.0 h	21:00	1023.3	18	5	4.92	0.02	0.02	23
2.5 h	21:30	1023.3	18	6.0 12 h test	5.9	0.02	0.02	23
14.5 h	Feb. 08, 2012 / 09:30	1022.8	17		7	6.86	0.02	0.02
15.0 h	10:00	1022.8	19	7.5	7.4	0.03	0.03	22
15.5 h	10:30	1022.8	20	8	7.92	0.03	0.03	21
16.0 h	11:00	1022.8	20	8.4	8.32	0.04	0.04	21
16.5 h	11:30	1022.9	20	8.6	8.52	0.04	0.04	21
17.0 h	12:00	1022.9	20	8.8	8.71	0.04	0.04	21
17.5 h	12:30	1022.4	20	9	8.92	0.05	0.05	21
18.0 h	13:00	1022.4	20	9.2	9.11	0.07	0.05	21
18.5 h	13:30	1021.4	20	9.4	9.32	0.08	0.07	21
19.0 h	14:00	1021.4	20	9.6	9.52	0.12	0.13	21
19.5 h	14:30	1020.8	20	9.8	9.72	0.18	0.22	21
20.0 h	15:00	1020.8	20	10	9.92	0.29	0.29	21
21.0 h	16:00	1020.8	20	9.6	9.53	0.13	x	21
24.0 h	19:00	1022.3	19		9.48	0.12		23
39.0 h	Feb. 09, 2012 / 10:00	1027.9	18	96 h test	9.4	0.09	x	23
42.0 h	13:00	1026.1	20		9.48	0.09		21
45.0 h	16:00	1025.5	20		9.48	0.1		21
48.0 h	19:00	1024.9	19		9.46	0.09		22
63.0 h	Feb. 10, 2012 / 10:00	1027.5	18		9.4	0.08		24

QC decision	Current Limits at 6.0 kV	RE4/2 TW	RE4/2 TN	RE4/2 BT	$i(14.5\text{h})$ at 6.0 kV	Final Decision	Certified	O	x						
	1.5 μA	1.5 μA	1.5 μA	0.02											
	RE4/3 TW	RE4/3 TN	RE4/3 B	1.5 μA	1.5 μA										
	1.5 μA	1.5 μA	1.5 μA	0.29											
	Current Limits at 10.0 kV	RE4/2 TW	RE4/2 TN	RE4/2 B	$i(20\text{h})$ at 10.0 kV										
	5.0 μA	5.0 μA	10.0 μA	5.0 μA	5.0 μA										
	RE4/3 TW	RE4/3 TN	RE4/3 B	5.0 μA	5.0 μA										
	5.0 μA	5.0 μA	10.0 μA	0.08											
	Current Limits at 9.6 kV at t = 120 h	RE4/2 TW	RE4/2 TN	RE4/2 B	$i(63\text{h})$						0.08				
	2.0 μA	2.0 μA	3.5 μA	$i(120\text{h})$	0.06										
	RE4/3 TW	RE4/3 TN	RE4/3 B	Criterion	$i(120\text{h})/i(63\text{h}) < 1.5$										
	2.0 μA	3.5 μA	5.0 μA	0.75											

**Set at 10.0 kV at  $t = 20.0$  h, and at 9.6 kV from 21 to 120 h for the long-term test.**

